

An Experimental Investigation of Structural and Electrochemical Performance of Al₅-Mo Thin Film Alloy Anodes for Li-ion Micro Batteries

¹S. Saravanan, ²R. Mahendran, ³A. Peramanan, ⁴P. Raj Kumar

Assistant Professor,

Department of Mechanical Engineering,
Jai Shriram Engineering College, Tirupur, TN, India¹

Abstract: The Al₅Mo thin film anodes for Li ion battery were prepared using DC sputtering method in different conditions like deposition at room temperature (S₀) and deposition at 350°C (S₁). The thin films were deposited from Aluminum target tiled with Molybdenum discs in the ratio calculated on the basis of theoretical sputtering yield. The structural analysis performed using XRD has confirmed the Al₅MO compound formation in rhombohedral geometry. The compound formation was observed to be evident only for the thin films when subjected to heat treatment while deposition. The scanning electron micrographs of the samples had revealed higher porosity around 24% for S₀ sample and lower porosity around 19% for S₁ sample. The chronopotentiometry results of the samples in non-aqueous electrolyte versus Li counter electrode had shown higher volumetric specific capacity around 198 mAh/cm³ for S₁ sample. The capacity increment had been observed for all the samples upon charge-discharge cycling and the extent of increment after 25 cycles for S₀ and S₁ samples were observed to be 41.2% and 20.4% respectively.

Keywords: Thin film anode, X-ray Diffraction, Scanning Electron Microscopy, Cycle life study.

I. INTRODUCTION AND EXPERIMENTAL

In most of the portable electronic equipment, Li ion secondary batteries are widely been deployed as power sources. Despite the implication of nano material electrodes, the extent of miniaturization of conventional Li ion batteries remains limited. At this juncture a research group led by J.B. bates and Nancy dudney et al from ORNL demonstrated solid state thin film Li ion batteries which attracted remarkable attention in late 90's [1,2]. The thin film batteries are viewed as futuristic power source by several researchers due to its efficacious performance and compatibility with IC components. In general, the theoretical specific capacities of the Li alloys are higher than the widely used lithiated graphite anode and slightly lesser than the metallic Lithium anode [3]. Widely investigated metal anodes include Al [4], Sn [5], Al-Sn alloy [6] and so on. Despite many advantages, the abnormal volume expansion while charging is observed to be common for all the metal anodes [7-9]. Hence in this paper the inclusion of electrochemically inactive Molybdenum (Mo) in to the Aluminum (Al) matrix has been investigated with the idea of alleviating the irreversible expansion occurring in the aluminum while charging. The Al-Mo intermetallic alloy anode thin films were prepared on copper substrate by DC magnetron sputtering process. The sputtering target was developed by new tiling method. The stoichiometric alloy was prepared by sputtering yield ratio calculation. Al₅Mo thin film was deposited in Cu substrate. The sputtering deposition from the target was achieved by applying the power of 85W and the films were coated to the approximate thickness of 2.0 μm. The thin film depositions were carried out with and without substrate heating up to 350°C. The structural analysis of the processed film was carried out by Philips PW 1710 diffractometer and the parameters were compared with standard JCPDS data. The morphological characterization of the film was analyzed by using JEOL, JSM – 6460 scanning electron microscopy. The electrochemical studies of the thin films of area 1cm² were studied by micro auto lab FRA III in non-aqueous electrolyte (1M LiPF₆ dissolved in 1:1 ratio of EC and DMC respectively) Vs. Li foil. The charge discharge analysis was carried out with the potential window of 2.1V to 3V at the current density of ±100μA/cm².

II. RESULTS AND DISCUSSION

The X ray diffractogram of thin film samples (i) deposited at room temperature without substrate heating (S₀), (ii) deposited at 300°C with substrate heating (S₁) are represented in Figure 1 and it is evident that the deposition in room temperature has not yielded crystalline thin films of either Al, Mo or their intermetallic. This may be attributed to the lack of nucleation in the cold substrate. Whereas, the samples S₁ have shown characteristic peak of Al₅Mo around 42.1 degrees (ICDD file No.65-1144) corresponding to (024) plane. The Cu substrate is observed around 51.18 degrees (ICDD file no. 89-2838) corresponding to (200) plane for both samples. Apart from the Al₅Mo and Cu substrate peak, another peak corresponding to Mo has occurred in sample S₁. This may be attributed to the precipitation of smaller volume of Mo in Al₅Mo matrix.

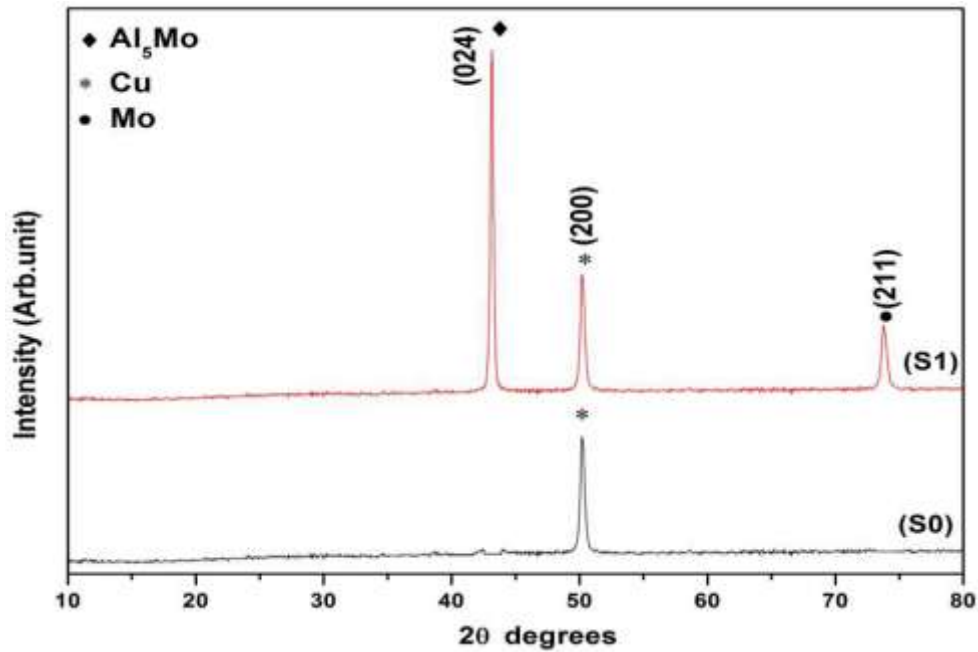


Figure 1: Structural analysis of deposited at room temperature (S₀) and deposited at substrate heating (S₁)

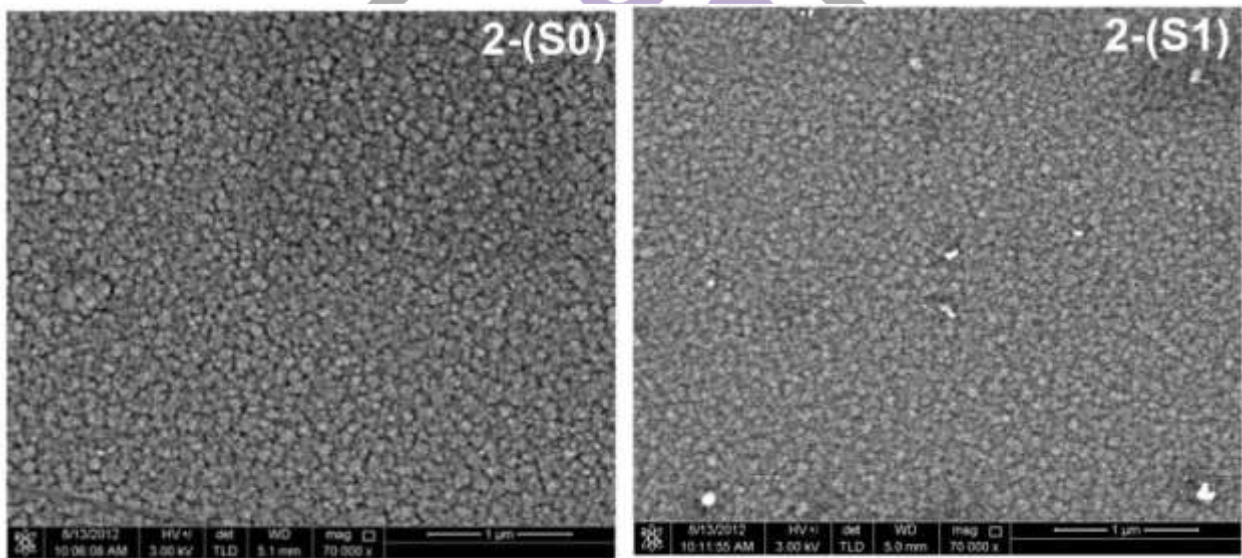


Fig. 2: Morphological analysis of deposited at room temperature (S₀) and deposited at substrate heating (S₁)

The scanning electron micrograph of the samples S₀ and S₁ are presented in Figure 2. From the figure, it could be observed that all the films possess homogeneously distributed smaller grains without significant grain agglomeration. The Figure 3 illustrates the charge discharge cycle study of samples S₀ and S₁ respectively. From the graph, the volumetric charging capacity of the samples could be calculated to be around 108.0 mAh/cm³ and 197.6 mAh/cm³ for the samples S₀ and S₁ respectively. The charge and discharge capacity are observed to be higher for S₁ sample which has been deposited in the temperature of 350°C using substrate heater. It may be due to the homogeneous distribution of Mo in Al₅Mo matrix.

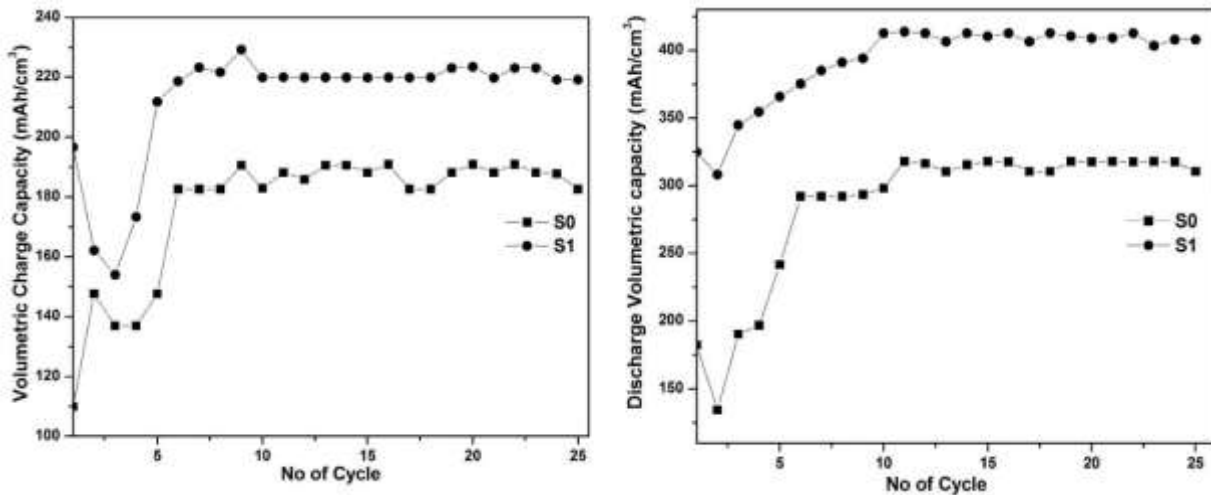


Figure 3: Charge and Discharge Cycle life study of Al₅Mo alloy thin films

From the figure 3, it could be observed that specific charge/discharge capacity increases for all the samples after 25 cycles. This may be attributed to the gradual increase in diffusion of Li ions into Al₅Mo matrix. The electrochemically inert Mo decreases the characteristic anomalous volume expansion of Al. The percentage discharge capacity increment after 25 cycles for the electrodes are observed to be around 41.2%, 20.4% and 21.1% for samples S₀ and S₁ respectively. The preparation of Al-Mo alloy thin film from through DC sputtering from indigenously tiled target has been exemplified in this manuscript. The X-ray diffraction results have further revealed the crystalline compound formation only due to the heat treatment during the deposition. From the Electrochemical Studies it could be concluded that the S₁ sample possess higher volumetric discharge capacity and which may corroborated to the homogeneous film formation due to heating while deposition. This work is actually intended to alleviate the anomalous irreversible volume expansion of Al anode occurring while charge- discharge cycles by the inclusion of electrochemically inactive Molybdenum (Mo) in to the Aluminum (Al) matrix.

REFERENCES

- [1] Bates.J.B, Dudney N.J, Gruzalski.G.R, Zuhr.R.A, Choudhury.A, C.F. Luck, Fabrication and characterization of amorphous lithium electrolyte thin films and rechargeable thin-film batteries, *Journal of Power Sources.*, 1993, 43, 103-110.
- [2] Bates.J.B, Gruzalski.G.R, Dudney.N.J, Luck.C.F, Rechargeable thin-film lithium batteries, *Solid State Ionics.*, 1994, 70, 619 - 628.
- [3] Wei-Jun Zhang., A review of the electrochemical performance of alloy anodes for lithium-ion batteries, *Journal of Power Sources.*, 2011,196, 13-24.
- [4] Lindsay.M.J, Wang.G.X, Liu.h.K, Al-based anode materials for Li-ion batteries, *Journal of Power Sources.*, 2003, 119, 84-87.
- [5] Wachtler.M, Besenhard.J.O, Winter.M, Tin and tin-based intermetallics as new anode materials for lithium-ion cells, *Journal of Power Sources.*, 2001, 94,189-193.
- [6] Hu.R.Z, Zhang.L, Liu.X, Zeng.M.Q, Zhu.M, Investigation of immiscible alloy system of Al-Sn thin films as anodes for lithium ion batteries, *Electrochemistry Communications.*, 2008, 10, 1109-1112.
- [7] Larcher.D., Beattie.S., Morcrette.S., Edstrom.K., Jumas.J.C., Tarascon.J.M., Recent findings and prospects in the field of pure metals as negative electrodes for Li-ion batteries, *Journal of Materials Chemistry.*, 2007, 17, 3759-3772.
- [8] Thackeray.M.M, Vaughney.J.Y, Fransson.L.M.L, Recent developments in anode materials for lithium batteries, *Journal of Materials Science.*, 2002, 54, 20-23.
- [9] Winter.M and Besenhard.J.O, Electrochemical lithiation of tin and tin-based intermetallics and composites, *Electrochemical Acta.*, 1999, 45, 31-50.